

Table 1. 75mm crushed concrete average percent passing and Kelowna specifications.

Seive Size (mm)	Average Percent Passing (%)	City of Kelowna Specifications	
		Min Spec	Max Spec
150.000	100.00	100.00	100.00
100.000	100.00	85.00	100.00
50.000	70.50	65.00	100.00
19.000	51.70	40.00	100.00
4.750	23.35	20.00	70.00
0.150	4.35	0.00	20.00
0.075	3.39	0.00	8.00

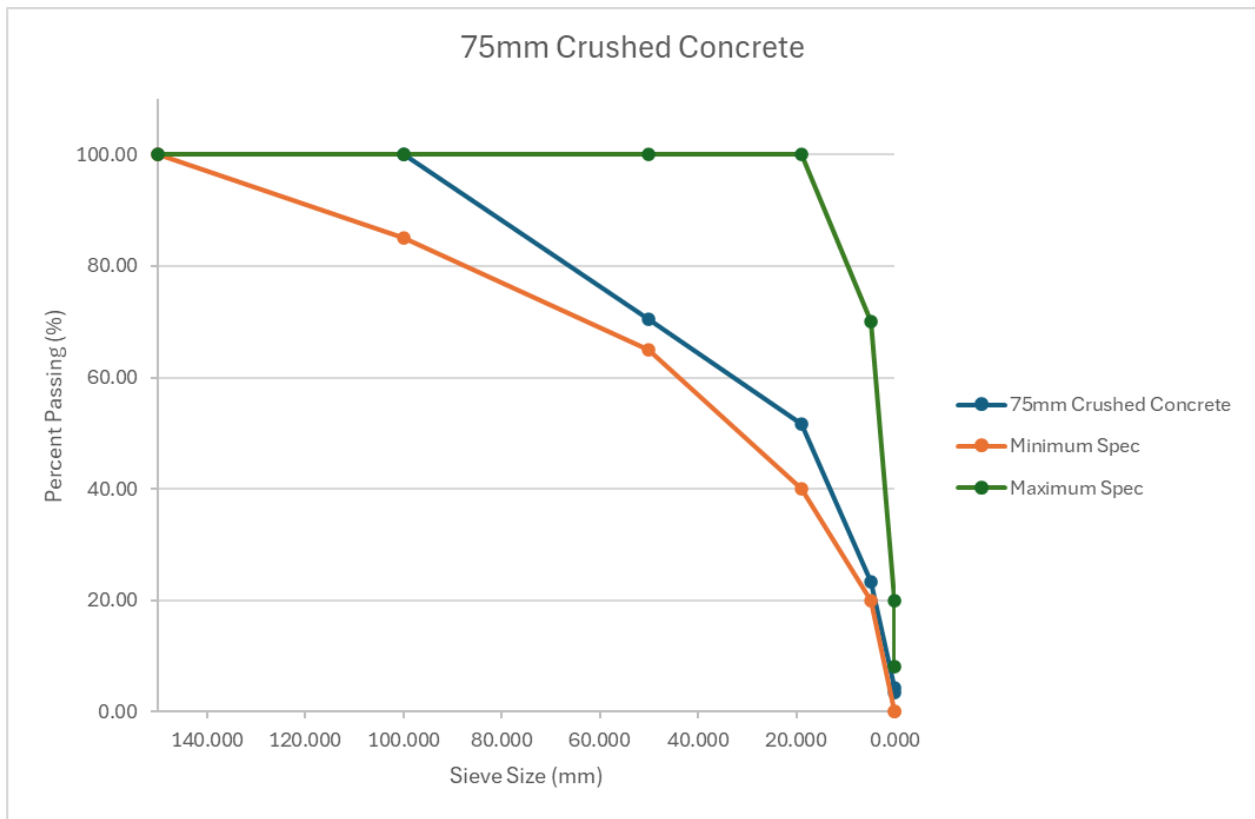


Figure 1. Relationship between percent passing (%) and sieve size (mm) for the average value of 75mm crushed concrete compared to City of Kelowna specifications.

Table 2. 19mm crushed asphalt average percent passing and Kelowna specifications.

Seive Size (mm)	Average Percent Passing (%)	City of Kelowna Specifications	
		Min Spec	Max Spec
25.000	100.00	100.00	100.00
19.000	100.00	80.00	100.00
9.500	64.47	60.00	90.00
4.750	39.27	35.00	70.00
2.360	28.73	25.00	50.00
1.180	17.20	15.00	35.00
0.300	8.30	5.00	20.00
0.075	3.80	2.00	8.00

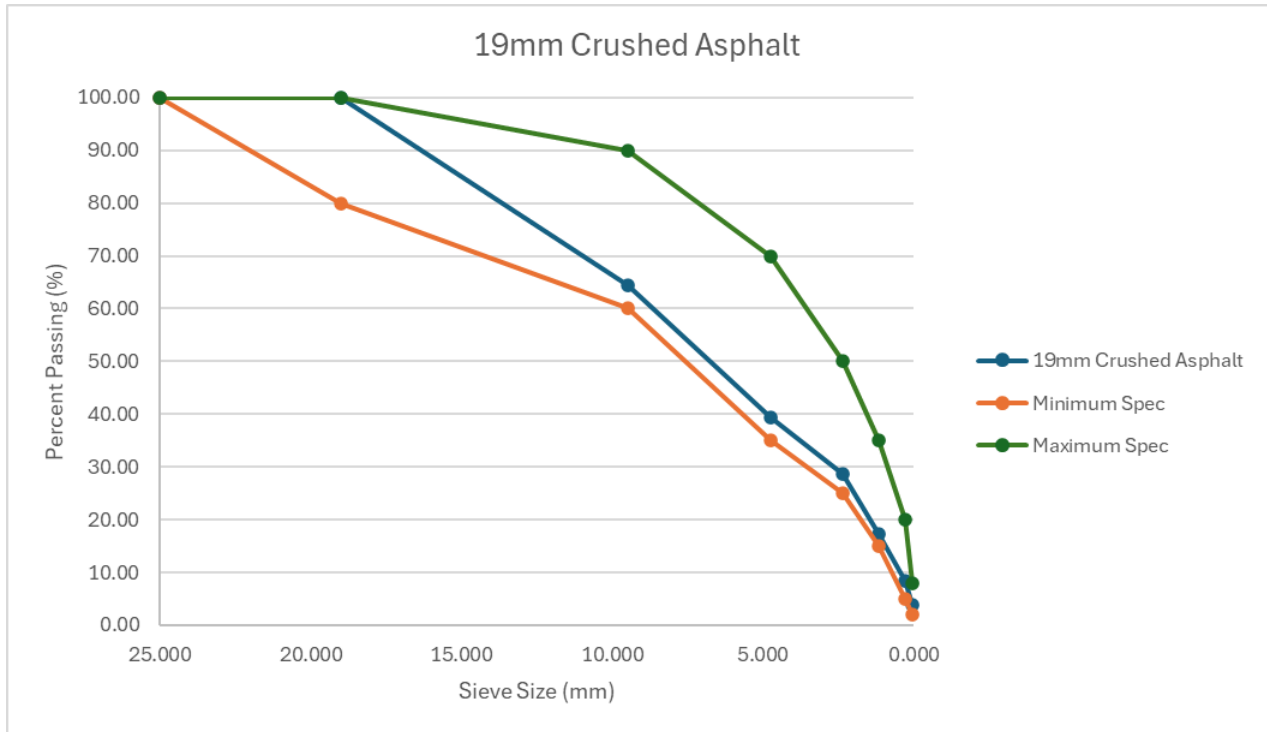


Figure 2. Relationship between percent passing (%) and sieve size (mm) for the average value of 19mm crushed asphalt compared to City of Kelowna specifications.

Table 3. 75mm crushed asphalt average percent passing and Kelowna specifications.

Seive Size (mm)	Average Percent Passing (%)	Coty of Kelowna Specifications	
		Min Spec	Max Spec
150.000	100	100.00	100.00
100.000	100	85.00	100.00
50.000	38.7	65.00	100.00
19.000	0	40.00	100.00
4.750	0	20.00	70.00
0.150	0	0.00	20.00
0.075	0	0.00	8.00

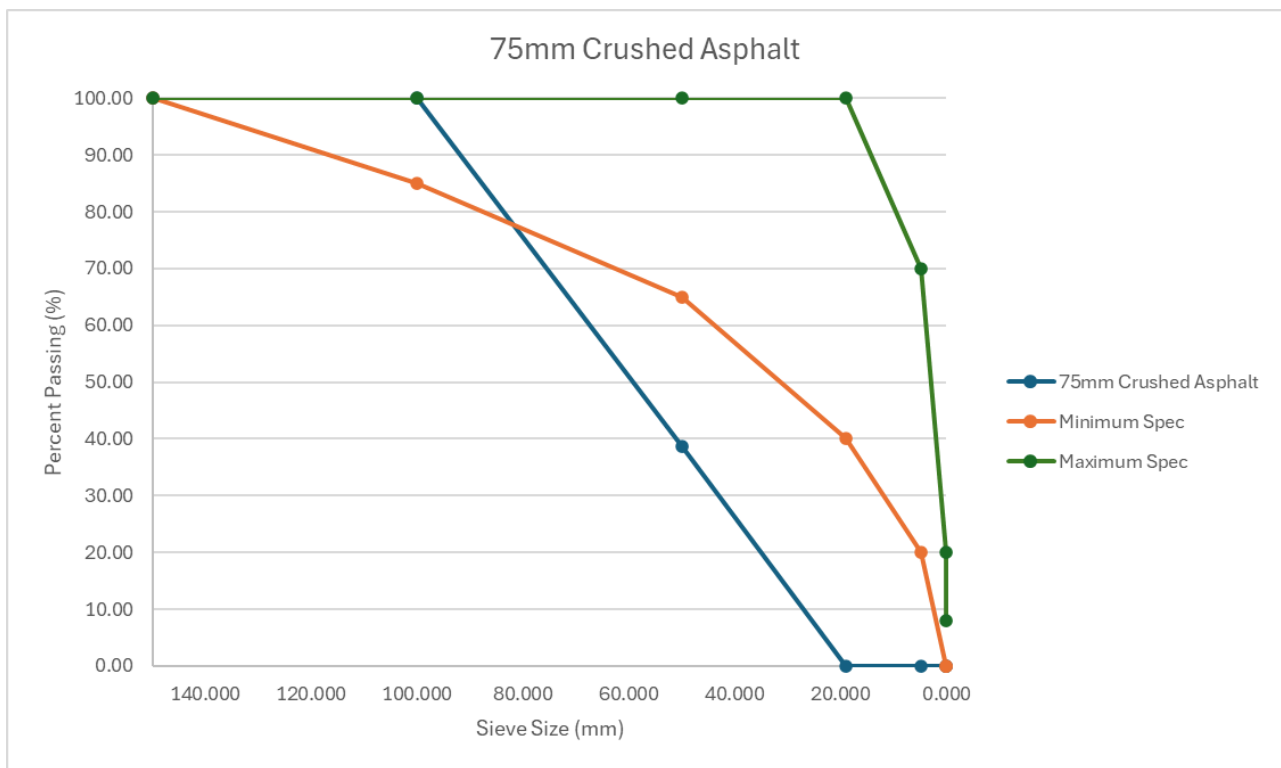


Figure 3. Relationship between percent passing (%) and sieve size (mm) for the average value of 75mm crushed asphalt compared to City of Kelowna specifications.